

WÜRTH ELEKTRONIK GMBH & CO. KG
SALZSTRASSE 21 74676 NIEDERNHALL GERMANY

Sample Description : PCB
Base Material Type : ISOLA - DE104
Solder Mask Type : PETERS - ELPEMER 2467

The above sample(s) data and information was / were submitted and identified on behalf of the client. SGS is not responsible for the authenticity, integrity and results of the data and information and / or the validity of the conclusion arising therefrom. Results apply to the sample as received.

SGS Ref. No. : SZIN2601000264PL01
Sample Receiving Date : Jan 28,2026
Testing Period : Jan 28,2026 to Feb 05,2026
Test Required : EN 45545-2:2020+A1:2023 Railway applications—Fire protection on railway vehicles Part 2: Requirements for fire behaviour of materials and components, and testing according to Table 5 — Material requirement sets (R24&R25)
Test result(s) : See attached sheet

Signed for and on behalf of
SGS-CSTC Standards Technical Services Co., Ltd. Shunde Branch

Ada

Ada Liu
Approved signatory



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1-2/F, Building 1, European Industrial Park, No.1, Shunhe South Road, Wusha, Daliang, Shunde District, Foshan, Guangdong, China 528300
中国·广东·佛山市顺德区大良街道办事处五沙社区居民委员会顺和南路1号欧洲工业园一号厂房首层、二层 邮编: 528300

t (86-757) 22805888 www.sgsgroup.com.cn
t (86-757) 22805888 sgs.china@sgs.com

I. Description of Test specimens

| | |
|--------------------|--|
| Sample Description | PCB |
| Size of specimens | T01 EN ISO 4589-2: 125 mm × 10.0 mm × 1.5 mm T16 EN60695-2-11: 60 mm × 60 mm × 1.5 mm |

II. Summary of test results

| Requirement set (used for) | Test method reference | Parameter Unit | Test results * |
|----------------------------|-----------------------------|--------------------------|----------------|
| R24 | T01 EN ISO 4589-2: OI | Oxygen content % | >60.0 |
| R25 | T16 EN 60695-2-11 | Glow Wire Temperature °C | 850 |

* For the test details, please see the appendix of this test report.

III. Conclusion

According to the test results, the submitted sample **met** the requirements of **R24& R25** (detailed in Table 5 of EN 45545-2:2020+A1:2023) for a **HL1, HL2, HL3** Hazard Level Classification.

Test Criteria for EN 45545-2:2020+A1:2023 Table 5 Material requirement sets (R24&R25)

| Requirement set (used for) | Test method reference | Parameter Unit | Requirement Definition | HL1 | HL2 | HL3 |
|----------------------------|-----------------------------|--------------------------|------------------------|-----|-----|-----|
| R24 (EL9) | T01 EN ISO 4589-2: OI | Oxygen content % | Minimum | 28 | 28 | 32 |
| R25 (EL9) | T16 EN 60695-2-11 | Glow Wire Temperature °C | Minimum | 850 | 850 | 850 |

Statements:

The test results relate to the behaviour of the test specimens of a product under the particular conditions of the test; they are not intended to be the sole criterion for assessing the potential fire hazard of the product in use.

The test results relate only to the specimens of the product in the form in which were tested.

The specimen was supplied by the sponsor and SGS-CSTC was not involved in any selection or sampling procedure.

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1-2/F, Building 1, European Industrial Park, No.1, Shunhe South Road, Wusha, Daliang, Shunde District, Foshan, Guangdong, China 528300

t (86-757) 22805888

www.sgsgroup.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙社区居民委员会顺和南路1号欧洲工业园一号厂房首层、二层 邮编: 528300

t (86-757) 22805888

sgs.china@sgs.com



Test 1:

T01 EN ISO 4589-2:2017 Determination of burning behaviour by oxygen Index Part 2: Ambient temperature test

1. Conditioning

T: (23±2) °C, R.H: (50±5)%, until the test sample was conditioned to constant mass.

2. Test results

- a) Select initial oxygen concentration(in accordance with 8.2.3): 25%
- b) Determining the Preliminary Oxygen Concentration(Till pair of oxygen concentrations which gives opposite response differs by ≤1%, in accordance with 8.6)

| | | | | | | | | |
|-------------------------------|------|------|------|------|------|--|--|--|
| Oxygen concentration, % (V/V) | 40.0 | 50.0 | 60.0 | 60.0 | 60.0 | | | |
| Burning period (s) | <180 | <180 | <180 | <180 | <180 | | | |
| Length burnt (mm) | <50 | <50 | <50 | <50 | <50 | | | |
| Response, ("X" or "O") | O | O | O | O | O | | | |

OI >60.0%

Burning behavior: Charring



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CS Standards Technical Services Co., Ltd.
Shunde Branch Inspection & Testing Services

1-2/F, Building 1, European Industrial Park, No.1, Shunhe South Road, Wusha, Daliang, Shunde District, Foshan, Guangdong, China 528300
中国·广东·佛山市顺德区大良街道办事处五沙社区居民委员会顺和南路1号欧洲工业园一号厂房首层、二层 邮编: 528300

t (86-757) 22805888 www.sgs.com.cn
t (86-757) 22805888 sgs.china@sgs.com

Test 2

T16 EN 60695-2-11: 2014 Fire hazard testing—Part 2-11:Glowing/hot-wire based test methods Glow-wire flammability test method for end-products

1. Conditioning

Prior to testing, the sample was conditioned 24 hours at temperatures of 15~35°C and at a relative humidity of 45~75%.

At time to testing, Temperature between 15°C ~ 35°C and Relative humidity less than or equal to 75 %.

2. Test results

| | |
|---|-----|
| Temperature of the glow-wire (°C) | 850 |
| Duration (t _i) from the beginning of tip application up to the time at which the test specimen or the specified layer placed below it ignites (s) | NI |
| Duration (t _e) from the beginning of tip application up to the time when flames extinguish during or after the period of application (s) | NI |
| Whether the test specimen extinguishes by virtue of most of the flaming material being withdrawn with the glow-wire | NA |
| Whether ignite the specified layer placed underneath the test specimen or not | No |
| Whether the test specimen is totally burned | No |
| Observations: NI | |

Remark: NI--- Not ignition; NA---Not applicable

In accordance with test results, the submitted sample: **GWEPT: 850**



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

1-2/F, Building 1, European Industrial Park, No.1, Shunhe South Road, Wusha, Daliang, Shunde District, Foshan, Guangdong, China 528300

t (86-757) 22805888


www.sgsgroup.com.cn

中国·广东·佛山市顺德区大良街道办事处五沙社区居民委员会顺和南路1号欧洲工业园一号厂房首层、二层 邮编: 528300

t (86-757) 22805888

sgs.china@sgs.com

Photo Appendix:

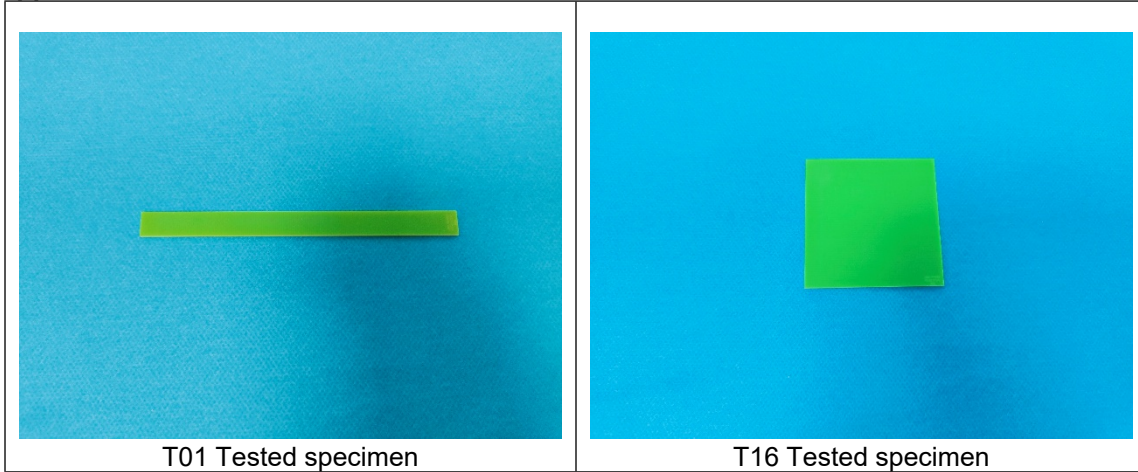

SGS authenticate the photo on original report only

End of Report



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <https://www.sgs.com/en/Terms-and-Conditions>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CS Standards Technical Services Co., Ltd.
Shunde Branch Inspection & Testing Services

1-2/F, Building 1, European Industrial Park, No.1, Shunhe South Road, Wusha, Daliang, Shunde District, Foshan, Guangdong, China 528300
中国·广东·佛山市顺德区大良街道办事处五沙社区居民委员会顺和南路1号欧洲工业园一号厂房首层、二层 邮编: 528300

t (86-757) 22805888 www.sgs.com.cn
t (86-757) 22805888 sgs.china@sgs.com